

Study of the Optical Properties of Magnesium Oxide Thin Films Using the Electro-Deposition Technique.

Morka, J.C.¹, Nwachuku, D.N.², & Okoye, O.V.³.

1,2 Physics Department, University of Delta, Agbor. Delta State, Nigeria.

3. Physics and Astronomy Department, University of Nigeria, Nsukka.

Article Information

Article # 10044
 Received: 24th Sept. 2024
 Revision: 28th Sept. 2024
 2nd Revision: 4th Oct. 2024
 Acceptance 11th Nov. 2024
 Available online:
 14th October, 2024.

Key Words

Optical, Electrodeposition,
 Magnesium Oxide,
 Absorbance,
 Thin Films

Abstract

Using $MgSO_4 \cdot 7H_2O$ as a starting precursor Magnesium oxide (MgO) thin films were effectively synthesised on Fluorine-doped Tin Oxide (FTO) glass substrates by electrode position method. By varying the deposition time, different thin films of thickness were prepared. An Ava-Spec-ULS 2048CL-2EV0 Spectrophotometer was used to obtain the absorbance spectra data. Other optical properties investigated from the calculation based on the data were, transmittance; Reflectance refractive index, thickness and band gap. Results obtained showed that MgO film thickness approximating $0.073\mu m$ to $0.125\mu m$ for films deposited within the time range of 0.5 minutes to 2.5 minutes respectively. The highest value of 0.21 abr unit was observed in the UV region for the absorbance. Transmittance value of about 61% and 94% were observed in the UV and NIR regions of the EMS respectively. Very high absorption coefficients (very low reflectance) were observed all through the UV-VIS NIR regions of the EMS. The thin films also recorded optical band gap, which ranged between 4.10 eV and 4.40 eV. The high transmittance value in the UV and NIR regions and the low reflectance of the MgO thin films make them suitable for optical applications and minimal light reflection respectively

*Corresponding Author: Morka, J.C. john.morka@unidel.edu.ng

Introduction

Magnesium oxide is a naturally occurring compound of Magnesium and oxygen. Its chemical formula is MgO and consists of a lattice of Mg^{2+} ions and O^{2-} ions held together by ionic bonding. Magnesium oxide (MgO) is a moderately high dielectric constant material (Nisatharaju *et al.*, 2014) with a very high band gap energy range of 4.50-5.25eV (Moses *et al.*, 2007). Magnesium oxide due to its unique properties is used in many applications such as ultraviolet (UV) photodetectors (Liao *et al.*, 2015), resistive switching (Samuel. *et al.*, 2023) and electrodes in pharmaceuticals and human fluids (Sultan *et al.*, 2016).

MgO doping has been shown to effectively inhibit grain growth in ceramics and improve their fracture toughness by transforming the mechanism of crack growth between 1-100 nanometers (nm) (Tan *et al.*, 2013).

In the past, several methods have been used to prepare MgO thin films and these are metal-organic decomposition (MOD) used to prepare Co ferrite thin films on MgO substrates (Minami *et al.*, 2015), Chemical Spray Pyrolysis technique used to deposit MgO nanostructured thin films with different thickness (Maher *et al.* 2021) and Spin – Coating technique used to fabricate MgO pure and doped with

Cerium thin films on Az31 alloy substrate (Ayse *et al.* 2015). This study represents the successful growth of MgO layers on FTO substrates via electrochemical deposition. The wavelength range covered in the analysis of the absorbance spectra was 300nm - 1100nm.

Materials and Methods

Electrodeposition involves the deposition of materials onto substrates from a solution containing charged particles, driven by an electric potential. In this study, FTO substrates were coated with MgO thin films using electrodeposition techniques by dissolving 12.5g of $MgSO_4 \cdot 7H_2O$ in 100ml of distilled water 0.5 M of magnesium sulphate ($MgSO_4 \cdot 7H_2O$) was prepared and this provided the needed Mg^{2+} ion for the synthesis of MgO thin films by dissolving 0.25g of citric acid (Hexane-1,2,3-tricarboxylic acid) in 100ml of distilled water by dissolving 5.00g of NaOH in 100ml of distilled water, 1M of sodium hydrate (NaOH) was prepared. This substance acted as both a chelating agent and a PH buffer. The dip solution's chemical components are summarized in Table 1 below. Before the deposition of magnesium oxide on the Fluorine-doped Tin Oxide (FTO) substrate, the FTO substrates were made to undergo solvent clearing, using acetone for about 20 minutes to dissolve and remove grease,

ultra-sonicated for about 15 minutes an ultrasonic bath and finally dried in a temperature-controlled drying oven.

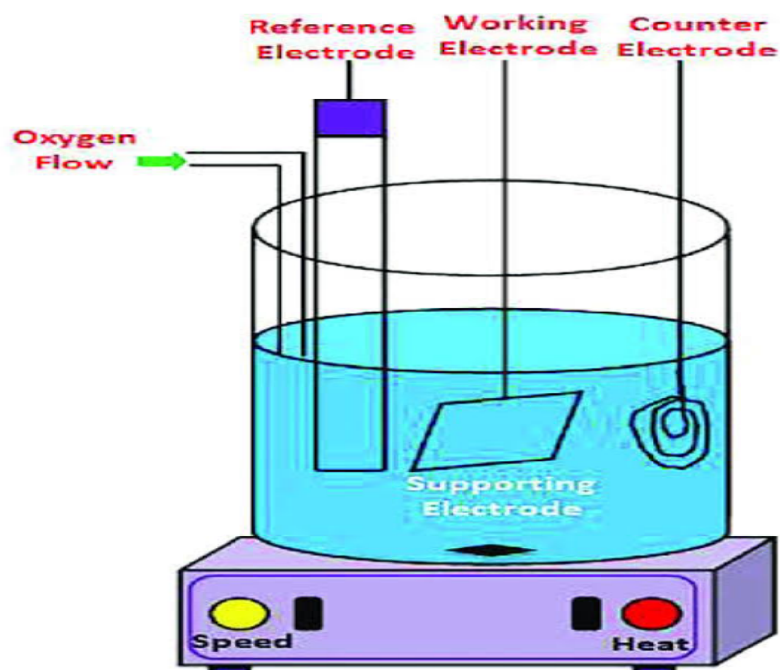


Figure 1: Diagram of the electrochemical deposition apparatus used in the experiment.

The components in the diagram are made up of the electrolytic cell (beaker), working electrode, anode (the electrode where oxidation occurs, platinum is used in this study), counter electrode (the electrode where reduction occurs), the power source DHRUVORO D'AZHENG PS-305D MODEL that drove the electrodeposition process, the saturated calomel electrode (SCE) used as the reference electrode, two digital multi-meters DT9Z01ACE model and thermometer (that was used to monitor the temperature

of electrolyte solution which is essential for controlling the electrodeposition process).

The absorbance spectra of the deposited films were subsequently recorded from Ava-Spec-ULS 2048CL-2EVO spectrophotometer in a wavelength range of 300nm-1100nm. Other optional properties such as transmittance reflectance refractive, index, optional thickness and band gap were calculated from known empirical relationships shown below as demonstrated by (Jania *et al*, 1979, Ozuomba and Ekpunobi, 2024, Kariperet *al*, 2018).

- (a) Transmittance (T), $T = 10^{-A}$, where A=absorbance
- (b) Reflectance (R), $R = 1 - (A + T)$
- (c) Refractive index (Γ) $= \frac{1 + R^{1/2}}{1 - R^{1/2}}$
- (d) Optical part length (Thickness (t)), $t = \left[\frac{1 - R^2}{T} \right] / \alpha$

Where α = Coefficient of absorption;

$$\alpha = \frac{A}{\lambda}$$

Where λ = wavelength

Table 1: Chemical composition for maximizing and minimizing of MgO deposition time.

Bath Name	Chemicals	Concentration (mol)	Volume (ml)	pH	Time of Deposition (mins)	Current I (mA)	Temperature (K)
MgO : A	MgSO ₄ . 7H ₂ O Citric acid NaOH	0.5 0.5 1.0	10.00 10.00 15.00	8.8	0.5	2.69	305
MgO : B	MgSO ₄ . 7H ₂ O Citric acid NaOH	0.5 0.5 1.0	10.00 10.00 15.00	8.8	1.0	2.52	305
MgO: C	MgSO ₄ . 7H ₂ O Citric acid NaOH	0.5 0.5 1.0	10.00 10.00 15.00	8.8	1.5	2.56	305
MgO: D	MgSO ₄ . 7H ₂ O Citric acid NaOH	0.5 0.5 1.0	10.00 10.00 15.00	8.8	2.0	2.39	305
MgO: E	MgSO ₄ . 7H ₂ O Citric acid NaOH	0.5 0.5 1.0	10.00 10.00 15.00	8.8	2.5	1.53	305

Results and Discussion

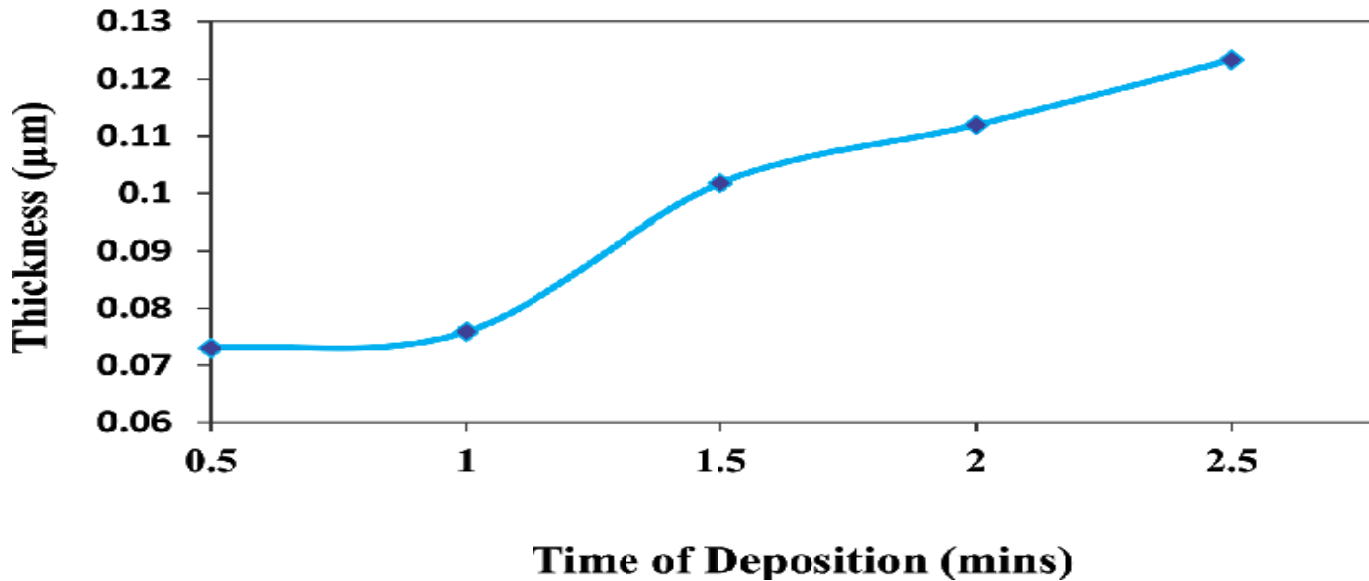


Figure 2: Graph of film thickness (µm) against time of deposition (mins) for MgO Thin film

Figure 2 showed that the film thickness specifically, for films deposited at 0.5 minutes and 2.5 minutes, the

thickness increased from about 0.073 µm to about 0.125 µm respectively.

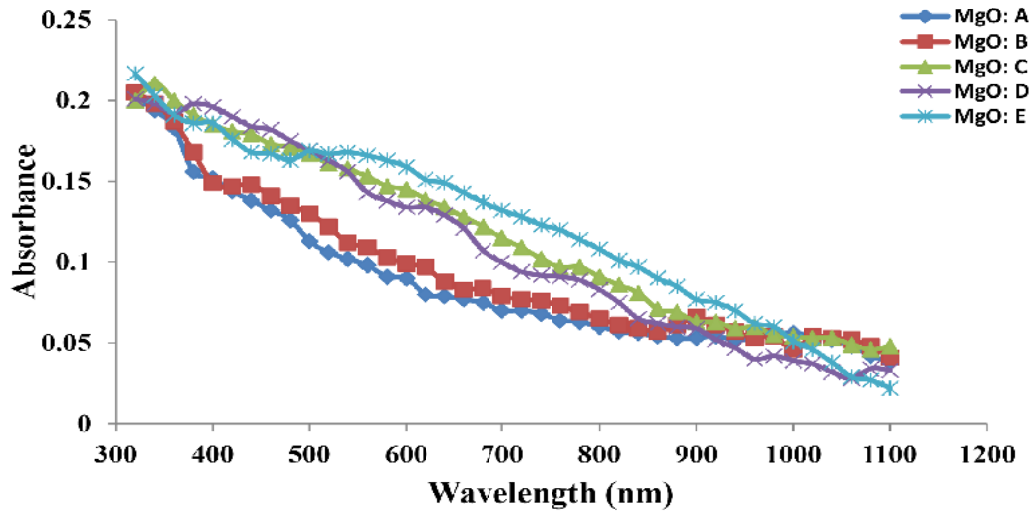


Figure 3: Graph of absorbance against wavelength for MgO Thin film

Figure 3 had the highest absorbance value of 0.21 abr unit in the UV region of the EMS. Generally,

absorbance decreased with an increase in wavelength, with very low values in the UV-Vis-NIR spectrum space.

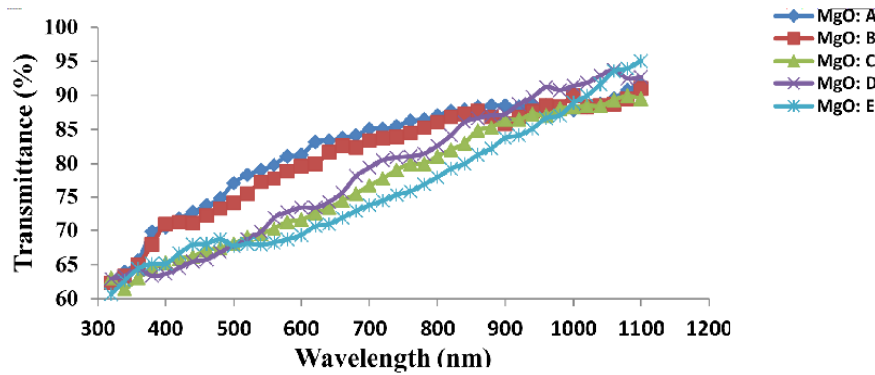


Figure 4: Graph of transmittance against wavelength for MgO Thin film

Figure 4 shows that transmittance increased with an increase in wavelength..The transmittance was high all through the spectrum range having about 60 % in the UV region and about 94 % in the NIR region.

The high transmittance of the deposited film position is for solar energy collection, because of coated on the surface of a collector, it will reduce the reflection of solar radiation and transmit radiation to the collector fluid (Egwunyenga *et al.*,2021)

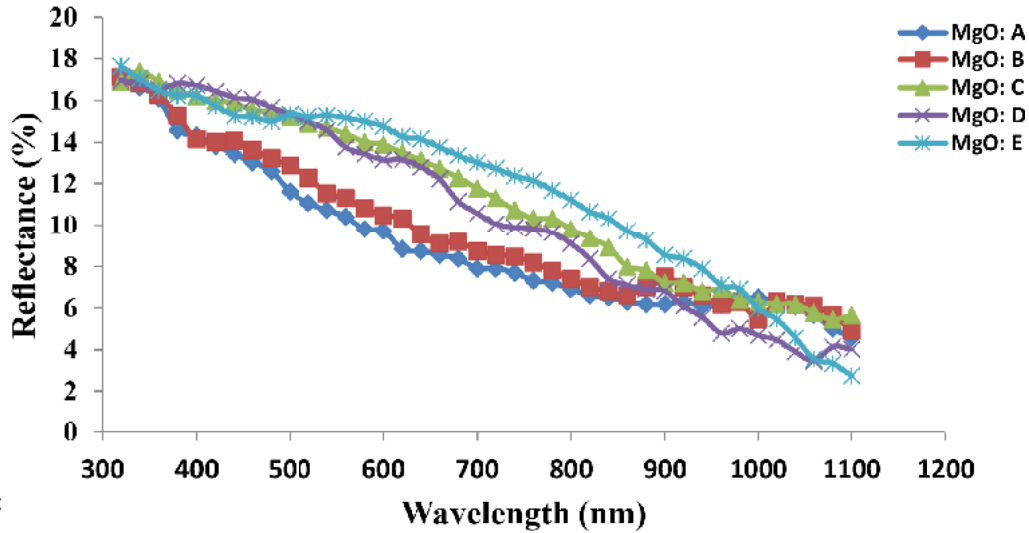


Figure 5:

Figure 5, shows that all the films had very low reflectance throughout the UV- VIS-NIR regions of the EMS with the highest value of 18% in the UV regions

This low reflectance value makes the MgO thin films suitable materials for anti-reflection coating. The films can also prevent excessive solar glare (Haruna *et al.*, 2015).

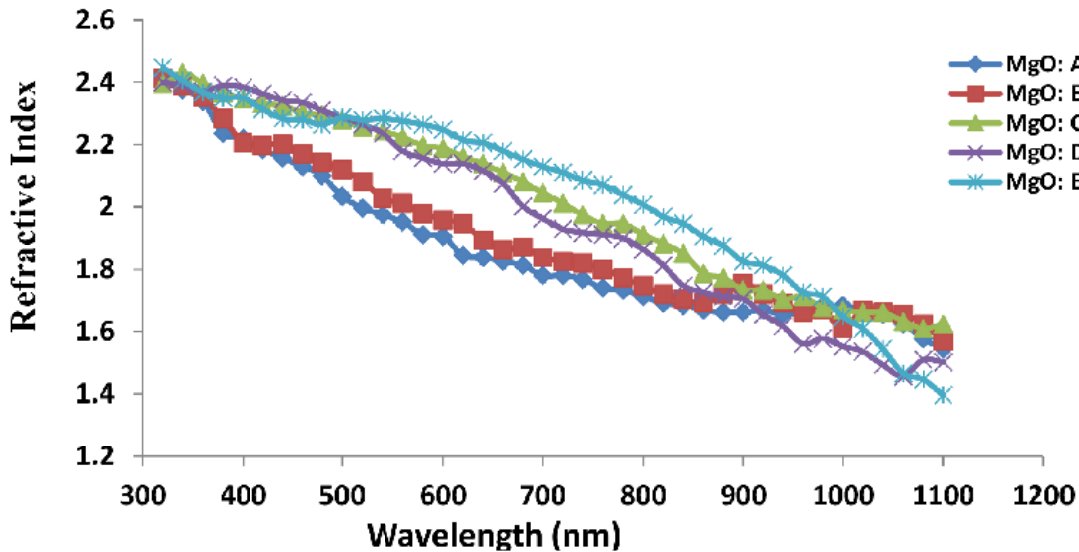


Figure 6: Graph of the refractive index against wavelength (nm) for MgO Thin film

Figure 6 showed that the refractive index of the MgO thin films decreased as the wavelength increased, with values of about 2.45 and 1.4 in the UV-VIS regions of the EMS, respectively. This high refractive index

makes the MgO thin films suitable for use in glass reflective coating as applied during the float process to enhance the amount of heat reflected by the glass (Ekwealor *et al.*, 2015)

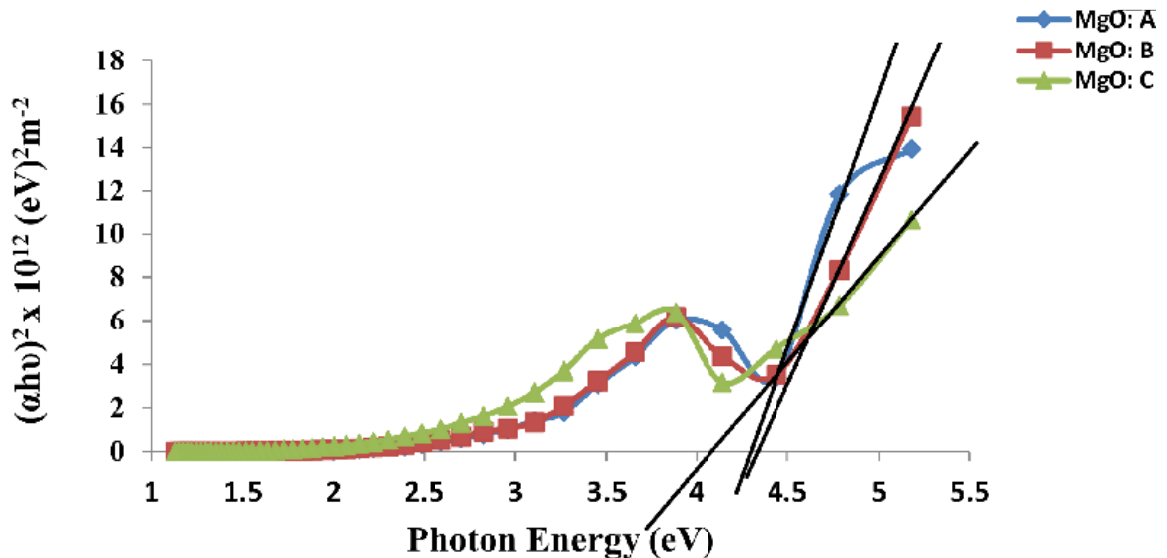


Figure 7: Graph of absorption coefficient squared against photon energy

Figure 7 shows the plot of the absorption coefficient squared ($\propto hv$)² against photon energy for MgO thin films for both MgO: A MgO: B and MgO: C respectively. The optical energy band gap was determined by extrapolating the straight-line part of the plot to the photon energy axis. The values of the band gap energy for MgO films deposited at A, B and C were 4.10 eV, 4.30 eV and 4.40 eV respectively.

Thus figure 7 revealed wide band gap energy values which ranged from 4.10 eV to 4.40 eV. These values of band gap energy are in line with values obtained by (Kokkonen *et al*; 2021).

The wide band gap recorded in this study positions the thin films as for coating of absorber layers of solar panels (Bart *et al.*, 2019).

Conclusion

In this study, MgO thin films were prepared using the electro-deposition technique under refined deposition conditions for optimal results. This study revealed that the electro-deposited magnesium oxide thin films exhibited exceptional optical properties, including a high refractive index ranging from 1.4 to 2.45 in the UV and NIR regions of the EMS respectively; and a wide optical band gap which ranged from 4.10 eV to

4.40 eV making them suitable for applications in ultraviolet photodetectors and optical sensors.

These findings demonstrate the potential of magnesium oxide thin films as a cost-effective and scalable material for advanced optical applications.

References

- Ayşe, K.B., Ozien, E., Nail, E. and Ibrahim, O. (2015). MgO and ZnO composite thin films using the Spin-coating method on microscope glasses. *Materials Sciences and Application*, 6, 40-47. <https://dx.doi.org/10.4236/msa.2015.61006>
- Bart, V, Marc, M, Guy, B, & Thomas, S. (2019). Wide band gap kesterite absorbers for thin film solar cells. Potential and challenges for their deployment in tandem devices. *Sustainable Energy and Fuels*, 3 (6), 1341-1590.
- Egwyunenga, N.J; Onu Buchi, V.C Okoli, N.L; and Nwankwo, L.E. (2021). Effect of solar cycles on the thickness, structural, and optical properties of cobalt selenide thin films. *International Research Journal of Multidisciplinary Tec novation*. 3(4), 1-9.

Ekwealor, A.B.C; Offia, S.U, Eze Ugo, S.C; and Ezema, F.I (2015). Variation of optical and structural properties of C_xO_y thin films with thermal treatment. *Indian Journal of Material Science*, 3(2), 180-191

Haruna, I; anladi, E, and Gyuk, P. (2015). Development of organic dye-sensitized solar cells incorporated with TiO_2 nanostructures with low conversion efficiency for exploring solar energy concepts. *International Journal of Optoelectronic Engineering*, 5(1), 16-19.

Janai, N Alfred, D. and Booth, D. and Seraphin, B. (1979). Optical properties and structure of amorphous silicon films prepared by chemical vapour deposition. *Journal of Solar Energy Materials*, 1, 11-27

Kari per, A Sadan, O. and Fatima, M.T. (2018). Optical Properties of selenium sulfide thin film produced via the chemical dropping method. *Optical and Quantum Electronics*. 50(12), 632-641.

Kokkonen, M Tale, P and Asgari, S. (2021). Advanced research trends in dye-sensitized solar cells. *Journal of Materials Chemistry*, 17, 373-386.

Liao, O Liang, M and Zhang, Z. (2015) strain-modulation and service behaviours of Au-MgO-ZnO ultraviolet photodetector by piezo-phototronic effect. *Nano-Research*, 8(12), 3772-3779.

Maher, T. Chayma, N. Badriyah, A. Chaker, B. Lass and, A., Neila, J., Ruxandra, V. and Najoua, T.K (2021). Synthesis and Characterization of MgO thin films obtained by spray technique for optoelectronic applications. *Nanomaterials*, 11, 3076-3086.
<https://doi.org/10.3390/nano11113076>

Minami, N Michi masa, S Takayuki, K. and Takayuki, B.S. (2015). Preparation and characterization of Co ferrite thin films on MgO (100) substrates by metal-organic decomposition. *Sensors and Materials*, 27(10), 925-931

Moses, A Ezhil, R Nehru, L.C. Jayachandran, M. and Sanjeevi raja, C. (2007). Spray pyrolysis deposition and characterization of highly (100) oriented magnesium oxide thin films. *Crystal Resource Technology*, 42, 867-877.

Nisatharaju, S Ayyappa, R and Balamurugan, D. (2014). Structural, morphological and optical characteristics of Spray deposited MgO thin films. *Asian Applied Science*, 7(8), 310-321.

Ozuomba, J. and Ekpunobi, A. (2014). Optical studies and photovoltaic performance of nanocrystalline titanium dioxide sensitized with local dye. *Journal of Nanostructure*, 4, 105-110

Samuel, C.W., Desmond, J.J., Siew, W.H. and Wen, S.L. (2023). Impact of interfacial engineering devices for low-power applications. *Applied Surface Science*. 608, <https://doi.org/10.1016/j.asusc.2022.155233>.

Sultan, A., Roshan, T., Bader, B.A. and Micheal, A.R. (2016). Investigation of the combined effect of MgO and PEG on the release profile of mefenamic acid prepared via hot-melt extrusion technique. *Pharmaceutical Development and Technology*, 22(6), 1-14.

Tan, C.Y, Yaghoubi A, Ramesh, S. Adzila, S., Purbolaksono, J Hasan. M.A and Kuttu, M.G (2013). Sintering and Mechanical Properties of MgO-deposited Nanocrystalline Hydroxyapatite. *Ceramics International* 39 (8), 867-877.